



International Journal for Innovative Engineering and Management Research

A Peer Reviewed Open Access International Journal

www.ijiemr.org

COPY RIGHT



ELSEVIER
SSRN

2021 IJEMR. Personal use of this material is permitted. Permission from IJEMR must be obtained for all other uses, in any current or future media, including reprinting/republishing this material for advertising or promotional purposes, creating new collective works, for resale or redistribution to servers or lists, or reuse of any copyrighted component of this work in other works. No Reprint should be done to this paper, all copy right is authenticated to Paper Authors

IJEMR Transactions, online available on 5th Sept 2021. Link

[:http://www.ijiemr.org/downloads.php?vol=Volume-10&issue=ISSUE-09](http://www.ijiemr.org/downloads.php?vol=Volume-10&issue=ISSUE-09)

DOI: 10.48047/IJEMR/V10/I09/56

Title **Synthesis of Polypyrrole/NiO Nanocomposites and their Properties**

Volume 10, Issue 09, Pages: 607-610

Paper Authors

P.Yamuna



USE THIS BARCODE TO ACCESS YOUR ONLINE PAPER

To Secure Your Paper As Per **UGC Guidelines** We Are Providing A Electronic Bar Code

Synthesis of Polypyrrole/NiO Nanocomposites and their Properties

P.Yamuna

Department of physics, Malla Reddy Engineering College (Autonomous), Hyderabad, Ts-500100.

Abstract

This study reports the synthesis of polypyrrole/NiO doped nanocomposites (NCs) as a shielding pigment in organic coatings. Polypyrrole/NiO doped NCs were prepared by in-situ chemical oxidative polymerization of pyrrole monomer. Here dopant NiO nanoparticles (NPs) were synthesized by solution combustion method using Aloe vera gel as fuel with ammonium per sulphate (APS) as oxidant. Different concentrations of NiO (10-50 wt%) NPs were incorporated into the polypyrrole. The synthesized nanocomposites were characterized for structural studies by means of powder X-ray diffraction (PXRD), and optical properties by UV-Visible Spectroscopy.

1. Introduction

Conductive polymers such as polyaniline (PANI), polypyrrole (PPy), and their composites are widely used as sensors [1, 2], energy storage materials, due to the facile synthesis and flexibility in processing [3]. Conducting polymers including polypyrrole (PPy), polyaniline (PANI), PPV, polyethylene dioxythiophene (PEDOT), and polythiophene (PT) have both electrochemical double layer capacitance and pseudo-capacitance arising from the fast and reversible oxidation and reduction processes related to their p-conjugated polymer chains [1-3]. Among these conducting polymers, PPy is outstanding as a promising electrode material for supercapacitors, because it has various significant advantages such as high specific capacitance, good conductivity, biocompatibility and outstanding mechanical properties [4]. However, like other electronically conducting polymers, PPy suffers from volumetric shrinkage during discharge process which can lead to decrease in cyclic stability [5-9]. To improve the cyclic stability of the conducting polymer, researchers have recently

synthesized various PPy-based composites with hierarchical structured materials to hinder the volume change of the conducting polymer during the charge-discharge processes [10-12]. As it is known to all, transition metal oxides have been massively reported as electrode materials for pseudo-capacitors because of their large capacitance and fast redox kinetics [3]. In this paper we report the synthesis of NiO nanoparticles using Aloe vera gel, synthesis of polypyrrole/Ni nanocomposites and their structural, morphological and optical studies in detail.

2. Experimental Methods

2.1 Synthesis of Polypyrrole

The synthesis of polypyrrole (PPy) was based on mixing aqueous solution of pyrrole and ammonium persulphate at ice temperature, followed by the separation of pyrrole precipitate by filtration and drying. An equimolar volume (0.1 M) of pyrrole and hydrochloric acid was dissolved in distilled water in a volumetric flask to obtain 100 mL of solution. Likewise, ammonium persulphate (0.2 M) was dissolved in

100 mL water. Both solutions were kept for 1 hour at room temperature and then mixed in a beaker, stirred with a mechanical stirrer and allowed to polymerizing. After a day, the PPy precipitate was collected using filter water, washed with acetone and deionised water repeatedly. The obtained polypyrrole powder was then dried in air in vacuum at 60 °C for 24 hours, then make it as a fine powder.

2.2 Synthesis of Polypyrrole/Nickel Oxide Nano-Composite

Synthesis of polypyrrole–nickel oxide nano-composites were carried out by in-situ polymerization method. Pyrrole (0.1 M) was mixed in 1 M HCl and stirred for 15 min. Nickel oxide nanoparticles were added in the mass fraction to the above solution with vigorous stirring in order to keep the nickel oxide homogeneously suspended in the solution. To this solution, 0.2 M of ammonium persulphate, which acts as an oxidizer was slowly added drop-wise with continuous stirring at ice temperature for 4 hours to completely polymerize. The precipitate was filtered, washed with de-ionized water and acetone, and finally dried in an oven for 24 hours to achieve a constant mass. The Polypyrrole -nickel oxide nano-composites were thus obtained containing various weight percentage of nickel oxide (i.e., 10, 20, 30, 40, and 50%).

3. Results and Discussion

3.1 XRD Analysis

X-Ray Diffraction studies were performed using Shimadzu-7000 diffractometer with Cu as the target (1.54 Å) and nickel as the filter. Fig. 1 shows X-ray diffraction pattern of polypyrrole. A broad peak centered at $2\theta = 25.53^\circ$ may be assigned to the scattering from the pyrrole

chains at interplanar spacing which clearly implies the amorphous nature of polypyrrole and it corresponds to diffraction planes (200) of pure polypyrrole and PPy/NiO nanocomposites. It was clearly observed from

the PXRD graph that pure PPy was in amorphous nature and as the NiO concentration increases from 30 wt% the amorphous nature partially disappear and crystallinity in the NCs were observed. It was evident that the NiO nanoparticles were completely interlocked between the polypyrrole chains. There were no additional impurity peaks were observed in XRD spectrum.

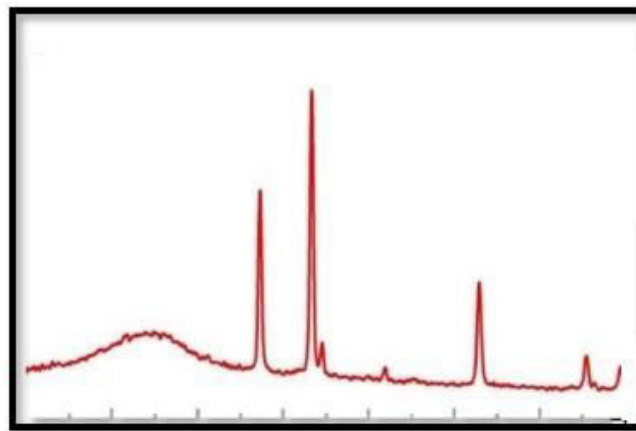


Fig. 1 XRD Pattern of PPy/ NiO nanocomposite

3.2 Optical Properties

The diffuse reflectance spectra (DRS) of pure and PPy/NiO 30 wt % were shown in Fig. 3. The Kubelka–Munk (K-M) theory was utilized to determine the energy band gap (E_g) synthesized PPy/NiO from DR spectra. where $R\%$ reflection coefficient of the sample, λ ; the absorption wavelength. The estimated E_g values 1.84 were mainly ascribed to degree of structural arrange and mess in the matrix as well as transform the distribution of energy levels within in the band gap.

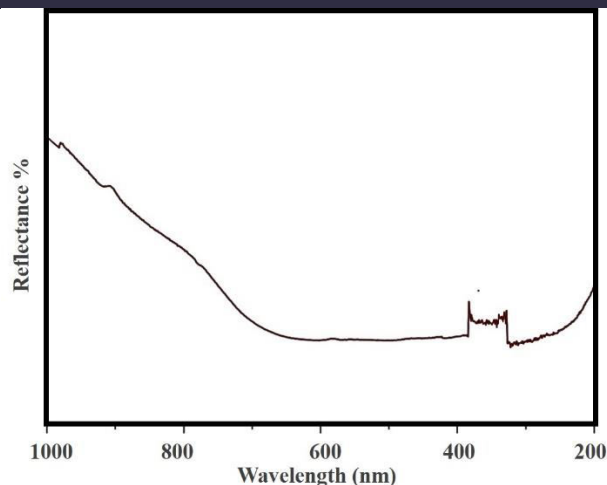


Fig. 2 DRS Pattern of PPy/ NiO nanocomposite

3. Conclusion

Pure and PPy/NiO NCs were successfully prepared by in-situ polymerization technique. The nanocomposites showed high crystalline nature with no impurity peaks. All these results together reveal that the synthesized composites can be used in the field of optical applications.

References

[1] H.K. Inamdar, H. Nagabhushana, B. Sannakki, R.D. Mathad, DC conductivity study of polyaniline/NiO nanocomposites prepared through green synthesis, *Mater. Today Proc.* 3 (2016) 3850-3854.

[2] R.L.N. Chandrakanthi, M.A. Careem, Preparation and characterization of CdS and Cu₂S nanoparticle/polyaniline composite films, *Thin Solid Films* 417 (2002) 51-56.

[3] S.M. Ambalgi, H.K. Inamdar, B. Sannakki, Materials mechanism of DC conductivity measurement of zinc oxide doped polyaniline, *Nanocomp. Today Proc.* 3 (2016) 3945-3950.

[4] Ali Fakhri, Sajjad Behrouz, Mohammad Asif, Inderjeet Tyagi, Shilpi Agarwal, Vinod Kumar Gupta, Synthesis, structural and

morphological characteristics of NiO nanoparticles co-doped with boron and nitrogen, *J. Mol. Liq.* 213 (2016) 326-331.

[5] Y. He, Synthesis of polyaniline/nano-CeO₂ composite microspheres via a solid-stabilized emulsion route, *Mater. Chem. Phys.* 92 (2005) 134-137.

[6] A.G. MacDiarmid, L.S. Yang, W.S. Huang, B.D. Humphrey, Polyaniline: electrochemistry and application to rechargeable batteries, *Synth. Met.* 18 (1987) 393-398.

[7] D. Verma, V. Datta, Role of novel microstructure of polyaniline-CSA thin film in ammonia sensing at room temperature, *Sens. Actuat. B* 134 (2008) 373-376.

[8] S. Farheen, F. Jahan, H.K. Inamdar, R.D. Mathad, Effect of polymer blending on mechanical and thermal properties, *Modern Appl. Sci.* 12(1) (2015) 520-522.

[9] S.M. Ambalgi, H.K. Inamdar, V.T. Manjula, S.G. Sannakki Nagaraja, Synthesis, characterization and electrical properties of polyaniline/nickel oxide nanocomposites, *Int. Jour. Eng. Res.* 5(2) (2016) 119-122.

[10] M.P. Pileni, Magnetic fluids: fabrication, magnetic properties, and organization of nanocrystals, *Adv. Funct. Mater.* 11 (2001) 323-336.

[11] S.C. Chen, T.Y. Kuo, T.H. Sun, Microstructures, electrical and optical properties of non-stoichiometric p-type nickel oxide films by radio frequency reactive sputtering, *Surf. Coat. Technol.* 205 (2010) S236-S240.

[12] J. Sort, J. Nogues, X. Amils, S. Surinach, J.S. Munoz, M.D. Baro, Room temperature magnetic hardening in mechanically milled ferromagnetic-antiferromagnetic composites, *J. Mag. Mag. Mater.* 219 (2000) 53-57.

[13] I. Hotovy, J. Huran, P. Siciliano, S. Capone, L. Spiess, V. Rehacek, The influences of preparation parameters on NiO thin film



International Journal for Innovative Engineering and Management Research

A Peer Reviewed Open Access International Journal

www.ijiemr.org

properties for gas-sensing application, Sens. Acut. B (2001) 126-132.

[14] R. Siddanna, H.K Inamdar, A. Mugalgaon, M.V.N. Ambikaprasad, Green 834.

synthesis of ZnO nanoparticles their structural and biological applications, Int.

J. Scien. Res. Sci. Eng. Technol. 4(1) (2018) 831-